

Mean-field heat capacity of dilute magnetic alloys

J. Maćkowiak*

*Universytet M. Kopernika, Instytut Fizyki, Grudziądzka 5,
87-100 Toruń, Poland*

February 6, 2008

PACS: 72.15.Qm, 75.10.Jm, 75.30.Hx

Abstract

Using an asymptotic solution of the M -impurity thermodynamics of a dilute s-d system, the impurity energy and impurity heat capacity $\Delta C(T)$ are derived for dilute magnetic alloys with spin 1/2 and spin 3/2 impurities. The parameters which enter ΔC are adjusted to fit experimental data on impurity heat capacity of CuCr and $(\text{La}_{1-x}\text{Ce}_x)\text{Al}_2$. Agreement is satisfactory for CuCr, at temperatures below 1K, and good for $(\text{La}_{1-x}\text{Ce}_x)\text{Al}_2$. The magnitude of theoretical $\Delta C(T)$ agrees with experiment and does not require scaling as in previous s-d theories. Nonlinear dependence of $\Delta C(T)$ on impurity concentration has been accounted for the first time.

1 Introduction

Existing theories of anomalous thermal behaviour of dilute magnetic alloys (DMA) (e. g. Refs. [1, 2, 3, 4, 5, 6, 7, 8, 9]) have provided only partial quantitative explanation of these anomalies. Most of these investigations were restricted to an s-d system consisting of a single magnetic impurity interacting with the electron gas.

Significant progress was made by Andrei et al. [4, 5], who solved the s-d thermodynamics for an s-d system with impurities treated as indistinguishable particles. Their heat capacity and magnetization curves, after scaling by an adjusted factor, provide a good fit to experimental data on $(\text{La}_{1-x}\text{Ce}_x)\text{Al}_2$.

The disadvantage of almost all existing theories of DMA is linear dependence of resulting thermodynamic functions on impurity concentration c . The dependence of DMA experimental data on c is more complex, e.g. the temperature at which DMA resistivity minimum occurs is proportional to $c^{1/5}$ [1] and normalized DMA impurity heat capacity $\Delta C/c$ is not constant in c [10].

*Email address: ferm92@fizyka.umk.pl

A different approach to the thermodynamics of DMA, in which the thermodynamic functions do not require rescaling and depend on c nonlinearly, was proposed by the author in Ref. [11]. The starting point in this approach is the first quantization s-d Hamiltonian $H_I^{(n,M)}$ describing n electrons and M distinguishable, arbitrarily positioned impurities with single-component spins interacting via a locally smeared s-d interaction $U(\vec{R}_\alpha - \vec{r}_i)S_{z\alpha}\sigma_{zi}$:

$$H_I^{(n,M)} = A^{(n)} \left(H_0^{(n)} + g^2 \sum_{\alpha=1}^M \sum_{i=1}^n U(\vec{R}_\alpha - \vec{r}_i) S_{z\alpha} \sigma_{zi} \right), \quad (1)$$

where $A^{(n)}$ denotes the antisymmetrizer with respect to electron variables with indices $i = 1, \dots, n$,

$$H_0^{(n)} = -\frac{\hbar^2}{2m} \sum_{i=1}^n \Delta_i. \quad (2)$$

$\vec{R}_\alpha$ denotes the position of α th impurity, $S_{z\alpha}$ its spin operator and $\vec{r}_i$, σ_{zi} the corresponding quantities of the i th electron. The considerations of Ref. [11] remain valid for any sufficiently regular function U depending on $|\vec{R}_\alpha - \vec{r}_i|$.

It was shown in Ref. [11], that in the dilute limit of small c (d-lim) the s-d interaction is separable and the system's free energy per electron $f(H_I^{(n,M)}, \beta)$ is equal asymptotically to that of n noninteracting electrons with the 1-electron Hamiltonian

$$h_e^{(1,M)}(\xi, \eta) = \tilde{h}_e^{(1,M)}(\xi, \eta) + \frac{1}{2}M(\xi^2 - \eta^2)\mathbb{I}, \quad (3a)$$

where

$$\tilde{h}_e^{(1,M)}(\xi, \eta) = H_0^{(1)} - g\sqrt{n}(\xi - \eta) \sum_{\alpha=1}^M U_\alpha^{(1)} \sigma_z^{(1)} \quad (3b)$$

and M impurities described by the Hamiltonian

$$h_{\text{imp}}^{(M)}(\xi) = g\sqrt{n}\xi \sum_{\alpha=1}^M S_{z\alpha} + \frac{1}{2}g^2 \sum_{\alpha=1}^M S_{z\alpha}^2. \quad (4)$$

$U_\alpha^{(1)}$ in Eq. (3b) is the multiplication operator by $U(\vec{R}_\alpha - \vec{r}_i)$ and $\eta(\xi) = \xi - f_2(\xi)$, with

$$f_2(\xi) = -\frac{g}{\sqrt{n}} \langle S_z \rangle_{h_{\text{imp}}^{(1)}}, \quad \langle B \rangle_h := \frac{\text{Tr}(B e^{-\beta h})}{\text{Tr} e^{-\beta h}}, \quad (5)$$

whereas ξ is the solution of the equation

$$\xi = f_1(f_2(\xi)) + f_2(\xi) \quad (6)$$

with

$$f_1(\xi) = g\sqrt{n} \left\langle \Gamma_1^n U_\alpha^{(1)} \sigma_z^{(1)} \right\rangle_{n\Gamma_1^n \tilde{h}_e^{(1,M)}(\xi, 0)}, \quad (7)$$

$$\Gamma_1^n B^{(1)} := A^{(n)} \left(B^{(1)} \otimes \mathbb{I}^{(n-1)} \right) A^{(n)},$$

which minimizes the mean-field free energy per electron $f(h^{(n,M)}, \beta)$, where

$$h^{(n,M)}(\xi, \eta) = h_e^{(n,M)}(\xi, \eta) + h_{\text{imp}}^{(M)}(\xi). \quad (8)$$

Asymptotic equivalence of $H_I^{(n,M)}$ and $h^{(n,M)}$ is expressed by the equality

$$\lim_{n \rightarrow \infty} \text{d-lim } f(H_I^{(n,M)}, \beta) = \lim_{n \rightarrow \infty} \text{d-lim } f(h^{(n,M)}, \beta) = \lim_{n \rightarrow \infty} f(A^{(n)} H_0^{(n)}, \beta). \quad (9)$$

The question arises, to what extent is the mean-field s-d Hamiltonian $h^{(n,M)}$ capable of providing a reliable theory of DMA thermal behaviour. Here a partial answer to this question is found by showing that impurity heat capacity curves of two CuCr alloys [10] with $c = 21.7$ ppm, 51 ppm and $(\text{La}_{1-x}\text{Ce}_x)\text{Al}_2$ [12] with $x = 0.0064$ can be satisfactorily explained in terms of $h^{(n,M)}$ thermodynamics.

To this end, the 1-particle equilibrium density operator $\rho^{(1)}$ of a quantum gas, in a field of randomly positioned wells, is first analysed in Section 2. Such operator appears, e.g. in the equation for the fugacity z :

$$\text{Tr } z \rho^{(1)} \left(\mathbb{I} + z \rho^{(1)} \right)^{-1} = n \quad (10)$$

where

$$\rho^{(1)} := \exp \left[-\beta \tilde{h}_e^{(1,M)}(\xi, 0) \right]$$

It is shown that, in the low-temperature régime, such a gas behaves effectively like a system of free particles at a temperature higher than that of the real system.

In Section 3 the mean-field impurity energy $\Delta U_{\text{s-d}}$ of the s-d system, relative to that of the free electron gas, is derived for impurity spins 1/2, 3/2. Here the crucial question is the form of f_1 . An approximate Sommerfeld-type expansion of $f_1(\xi)$ is found, which is subsequently applied in the simplest truncated form, viz., $f_1(\xi) = b_0 + b_1 \xi$, with $b_0, b_1 \in \mathbb{R}^1$. As a consequence, $\Delta U_{\text{s-d}}$ depends on five parameters: $b_0, b_1, g, M, \Delta T$, M denoting the number of impurities in the considered s-d subsystem of the molar s-d system and $\Delta T > 0$ the shift in temperature scale due to random interactions unaccounted for by the s-d Hamiltonian (1).

The expression for the mean-field heat capacity

$$\Delta C(T) = \frac{\text{d} \Delta U_{\text{s-d}}}{\text{d} T} \quad (11)$$

was calculated analytically and the parameters $b_0, b_1, g, M, \Delta T$ adjusted to obtain directly the best possible fit of mean-field $\Delta C(T)/c$ with experimental data, without additional rescaling procedures.

Variation of $\Delta C/c$ with c [10] requires different values of $b_0, b_1, g, M, \Delta T$ for different impurity concentrations. In this manner, for the first time, nonlinearity of $\Delta C(T)/c$ with respect to c has been accounted for.

2 1-particle density operator of a quantum gas in a field of randomly positioned wells

The Hamiltonian $H_I^{(n,M)}$ gives only a simplified account of the interactions present in an s-d system. It does not contain terms representing the Coulomb interactions between electrons and the screened Coulomb pseudo-potential $\sum_{\alpha} U_{C\alpha}$ of each electron in the field of impurities. In order to investigate the effect of such potential on the electron gas in a DMA, let us examine the 1-particle density operator of a gas of negatively charged particles interacting with randomly positioned positively charged ions in a region Λ .

Let

$$h^{(1)} = -\frac{\hbar^2}{2m}\Delta + \sum_{\alpha} U_{C\alpha}^{(1)} \quad (12)$$

denote the 1-particle Hamiltonian. Suppose U_C is a sufficiently regular function of $|\vec{R}_{\alpha} - \vec{r}|$, so that the integral kernel of $\rho^{(1)} = \exp[-\beta h^{(1)}]$ admits the Feynman-Kac representation [13, 14], viz.,

$$\rho(\vec{r}, \vec{r}') = \int_{\Omega_0} d\mu_{\vec{r}, \vec{r}'}(\omega) \exp \left[-\sum_{\alpha} \int_0^{\beta} U_{C\alpha}(\omega(s)) ds \right] \quad (13)$$

where $U_{C\alpha}(\vec{r}) = U_C(\vec{R}_{\alpha} - \vec{r})$. Due to randomness of ion positions $\vec{R}_{\alpha}$, $\rho(\vec{r}, \vec{r}')$ is equal to its space average $\langle \rho(\vec{r}, \vec{r}') \rangle_{\Lambda}$ over these positions [15, 16]. In order to evaluate $\langle \rho(\vec{r}, \vec{r}') \rangle_{\Lambda}$, let us note that $U_{C\alpha}$ is negative-valued and has a finite minimum [17]. Suppose it admits a Taylor expansion in the neighbourhood of this minimum at $\vec{r}_{0\alpha}$ and that β is sufficiently large. Then

$$\langle \rho(\vec{r}, \vec{r}') \rangle_{\Lambda} = |\Lambda|^{-M} \prod_{\alpha=1}^M \int_{\Lambda} d^3 R_{\alpha} \rho(\vec{r}, \vec{r}') \quad (14)$$

can be evaluated by expanding $U_C(\vec{R}_{\alpha} - \vec{r})$ up to second order and applying the method of steepest descent. Evaluation of the average (14) thus amounts to calculating the integral

$$\prod_{\alpha} \int_{\Lambda} d^3 R_{\alpha} \exp \left[-\beta u_0 - \frac{1}{2} u_2 \int_0^{\beta} \sum_{q=1}^3 (R_{\alpha q} - r_{0\alpha q} - \omega_q(s))^2 ds + \dots \right] \quad (15)$$

where $u_0 = U_C(\vec{R}_{\alpha} - \vec{r}_{0\alpha})$, $u_2 = U_C''(\vec{R}_{\alpha} - \vec{r}_{0\alpha})$. This is done in Appendix A.

One obtains for sufficiently large β

$$\begin{aligned} \left\langle \rho \left(\vec{r}, \vec{r}' \right) \right\rangle_{\Lambda} &= Z_1 \int_{\Omega_0} d\mu_{\vec{r}, \vec{r}'}(\omega) \int_{\mathbb{R}^3} \exp[-\beta M u_0 \\ &\quad - \frac{1}{2} M u_2 \sum_{q=1}^3 \int_0^{\beta} (\omega_q(s) - \lambda_q)^2 ds] d\lambda_1 d\lambda_2 d\lambda_3 \end{aligned} \quad (16)$$

where

$$Z_1 = |\Lambda|^{-M} \left(\frac{2\pi}{\beta u_2} \right)^{\frac{3}{2}(M-1)} M^{3/2}$$

The integral kernel (16) thus represents, up to a constant factor, the kernel of the canonical density operator of a particle oscillating around a point $\vec{\lambda}$, integrated over all positions $\vec{\lambda} \in \mathbb{R}^3$. In other words,

$$|\Lambda|^{-M} \prod_{\alpha} \int_{\Lambda} d^3 R_{\alpha} \rho^{(1)} = Z_1 \exp[-\beta M u_0] \int_{\mathbb{R}^3} d^3 \lambda \exp[-\beta h_{\text{osc}}^{(1)}(\vec{\lambda})] \quad (17)$$

where

$$h_{\text{osc}}(\vec{\lambda}) = -\frac{\hbar^2}{2m} \Delta + \frac{1}{2} M u_2 \left(\vec{r} - \vec{\lambda} \right)^2. \quad (18)$$

The integral kernel of $\exp[-\beta h_{\text{osc}}^{(1)}(\vec{\lambda})]$ is [13, 14, 18]

$$\rho_{\text{osc}}(\vec{r}, \vec{r}') = \xi^3 \exp \left[-\frac{1}{2} a \left[\left(\vec{r} - \vec{\lambda} \right)^2 + \left(\vec{r}' - \vec{\lambda} \right)^2 \right] + b \left(\vec{r} - \vec{\lambda} \right) \left(\vec{r}' - \vec{\lambda} \right) \right] \quad (19)$$

with

$$\xi = \frac{\alpha \left(\tanh \frac{1}{2} \Omega \right)^{1/2}}{2\sqrt{\pi} \sinh \frac{1}{2} \Omega}, \quad a = \alpha^2 \coth \Omega, \quad b = \frac{\alpha^2}{\sinh \Omega},$$

$$\alpha^2 = \hbar^{-1} \sqrt{M m u_2}, \quad \Omega = \frac{\hbar^2 \alpha^2}{m} \beta.$$

The integral over $\mathbb{R}^3$ on the rhs of Eq. (16) is thus a product of three 1-dimensional integrals

$$\begin{aligned} &\int_{-\infty}^{\infty} d\lambda \exp \left[-\frac{1}{2} a \left[(x - \lambda)^2 + (x' - \lambda)^2 \right] + b (x - \lambda) (x' - \lambda) \right] \\ &= \sqrt{\frac{\pi}{a - b}} \exp \left[-\frac{1}{4} (a + b) (x - x')^2 \right] \end{aligned} \quad (20)$$

each of which is equal to the integral kernel of the operator [13, 14]

$$\sqrt{\frac{\pi}{a - b}} \sqrt{2\pi t_0} \exp[-t_0 T_0] = \frac{2\pi}{\sqrt{a^2 - b^2}} \exp[-t_0 T_0], \quad (21)$$

where

$$t_0 = \frac{2}{a+b} = 2\alpha^{-2} \tanh \frac{1}{2}\Omega \quad , \quad T_0 = -\frac{1}{2} \frac{d^2}{dx^2}.$$

One finds

$$t_0 T_0 = t(u_2, \beta) \left(-\frac{\hbar^2}{2m} \frac{d^2}{dx^2} \right) = t(u_2, \beta) H_{0x}^{(1)} \quad (22)$$

with

$$t(u_2, \beta) = \delta^{-1} \tanh(\delta\beta) \quad , \quad \delta = \frac{\hbar^2}{2m} \alpha^2.$$

Combining Eqs. (16), (20), (21), (22), one obtains for large β the asymptotic equality

$$\left\langle \rho(\vec{r}, \vec{r}') \right\rangle_{\Lambda} = Z_0(u_0, u_2) (2\pi t_0)^{-3/2} \exp \left[-\frac{1}{2t_0} (\vec{r} - \vec{r}')^2 \right], \quad (23)$$

where

$$Z_0(u_0, u_2) = |\Lambda|^{-M} \left(\frac{2\pi}{\beta u_2} \right)^{\frac{3}{2}(M-1)} M^{3/2} \xi^3 \left(\frac{2\pi}{\alpha^2} \right)^3 \exp[-\beta M u_0].$$

Thus

$$\left\langle \rho^{(1)} \right\rangle_{\Lambda} = Z_0 \exp \left[-t H_0^{(1)} \right] \quad (24)$$

In the low-temperature régime, $\left\langle \rho^{(1)} \right\rangle_{\Lambda}$ is thus equal, up to a normalization factor, to the canonical density operator of a free particle at an effective temperature $(k_B t)^{-1} > (k_B \beta)^{-1} = T$.

3 Mean-field impurity heat capacity

Formulae for s-d system's mean-field energy ΔU_{s-d} and heat capacity ΔC , relative to that of free electrons, will be now derived, using the Hamiltonian $h^{(n,M)}$, and compared with experimental data on impurity heat capacity of CuCr [10] and LaCeAl₂ [12].

3.1 CuCr alloys

According to Monod et al. [19] the spin of the Cr³⁺ ions in CuCr alloys equals 3/2. The impurity expectation energy in these alloys therefore equals

$$\begin{aligned} U_{\text{imp}} &= \left\langle h_{\text{imp}}^{(M)} \right\rangle_{h_{\text{imp}}^{(M)}} \\ &= -Mn\xi f_2(\xi) + \frac{1}{2}Mg^2 + 4Mg^2 \frac{e^{-4\beta g^2} \cosh(3\beta g\xi\sqrt{n})}{e^{-4\beta g^2} \cosh(3\beta g\xi\sqrt{n}) + \cosh(\beta g\xi\sqrt{n})}. \end{aligned} \quad (25)$$

f_1 , defined by Eq. (7) is a linear function in the simplest approximation (45): $f_1(\xi) = b_0 + b_1\xi$ (Appendix B). Then according to Eqs. (42), (44), the interaction energy of electrons with the Hamiltonian $\tilde{h}_e^{(n,M)}(\xi, \eta)$ equals

$$\begin{aligned}\Delta U_e &= \left\langle \tilde{h}_e^{(n,M)}(\xi, \eta) \right\rangle_{\tilde{h}_e^{(n,M)}(\xi, \eta)} - \left\langle A^{(n)} H_0^{(n)} \right\rangle_{A^{(n)} H_0^{(n)}} \\ &= -Mn f_2(\xi) (b_0 + b_1 f_2(\xi) + \dots).\end{aligned}\quad (26)$$

From Eqs. (8), (25), (26) one obtains the following expression for ΔU_{s-d} of a system of n electrons and M impurities with spin 3/2:

$$\Delta U_{s-d} = U_{\text{imp}} - Mn f_2(\xi) (b_0 + b_1 f_2(\xi) + \dots) + Mn \xi f_2(\xi) - \frac{1}{2} Mn f_2^2(\xi) \quad (27)$$

where ξ is the minimizing solution of Eq. (6) with f_1 given by Eq. (45).

The number of conduction electrons per host atom in CuCr equals one, and hence the number of these electrons per impurity $n_1 = c^{-1}$.

The n -electron, M -impurity s-d system will be now treated as a subsystem of a sample S containing one mole of impurities. Then $n = Mn_1$. In terms of n_1 , $\gamma = \sqrt{M}g$, the energy $\Delta U_m = 6.022 \cdot 10^{23} M^{-1} \Delta U_{s-d}$ of such sample with spin 3/2 impurities, divided by c and expressed in joules, equals

$$\begin{aligned}c^{-1} \Delta U_m &= \left(\frac{1}{2} \gamma^2 + 4\gamma^2 \frac{e^{-4\beta\gamma^2 M^{-1}} \cosh(3\beta\gamma\xi\sqrt{n_1})}{e^{-4\beta\gamma^2 M^{-1}} \cosh(3\beta\gamma\xi\sqrt{n_1}) + \cosh(\beta\gamma\xi\sqrt{n_1})} \right. \\ &\quad \left. - \frac{1}{2} M^2 n_1 f_2^2(\xi) - M^2 n_1 f_2(\xi) (b_0 + b_1 f_2(\xi) + \dots) \right) 602.2 \cdot 160.2 M^{-1} n_1\end{aligned}\quad (28)$$

with

$$f_2(\xi) = \frac{\gamma}{M\sqrt{n_1}} \frac{3e^{-4\beta\gamma^2 M^{-1}} \sinh(3\beta\gamma\xi\sqrt{n_1}) + \sinh(\beta\gamma\xi\sqrt{n_1})}{e^{-4\beta\gamma^2 M^{-1}} \cosh(3\beta\gamma\xi\sqrt{n_1}) + \cosh(\beta\gamma\xi\sqrt{n_1})}$$

if γ, b_0 are given in $\sqrt{\text{eV}}$.

Eq. (6) takes the form

$$f_3(\xi) = \xi \quad (29)$$

with $f_3 = b_0 + (b_1 + 1) f_2$.

The excess heat capacity of S , relative to that of pure Cu, equals

$$\Delta C(T) = \frac{\partial \Delta U_m}{\partial T} + \frac{\partial \Delta U_m}{\partial \xi} \frac{\partial \xi}{\partial T}, \quad (30)$$

where

$$\frac{\partial \xi}{\partial T} = -\frac{\partial f_3}{\partial T} \left(\frac{\partial f_3}{\partial \xi} - 1 \right)^{-1}. \quad (31)$$

$\Delta C(T)$ depends on the solution ξ of Eq. (29) and on the parameters b_0, b_1, γ, M . An additional parameter $\Delta T > 0$, equal to the shift of the temperature variable of ΔC , proves necessary. The origins of this shift are explained in Section 2.

Alloy	x	c	n_1	b_1	$b_0 [\sqrt{\text{eV}}]$	$\gamma [\sqrt{\text{eV}}]$	M	$\Delta T [\text{K}]$
CuCr	-	$\frac{51}{10^6}$	$\frac{10^6}{51}$	-461	$1.09 \cdot \frac{10^{-3}}{n_1^3}$	0.091	248500	1.05
CuCr	-	$\frac{212}{10^7}$	$\frac{10^7}{212}$	-631	$1.01 \cdot \frac{10^{-3}}{n_1^3}$	0.086	$36 \cdot 10^4$	0.78
(LaCe) Al ₂	$\frac{64}{10^4}$	$\frac{4}{1871}$	$\frac{3742}{3}$	-13101	$\frac{19}{10^5}$	$\frac{31}{10^5}$	58	0.39

Table 1:

The best fitting graphs of $c^{-1}\Delta C(T + \Delta T)$ vary with M . Moreover, the graphs obtained for $M \gg 1$ provide much better agreement with experiment than those for $M = 1, 2$. The graphs of $c^{-1}\Delta C(T + \Delta T)$ for CuCr with $c = 51$ ppm ($M = 24850$) and $c = 21.2$ ppm ($M = 360000$), plotted in the same units as in Ref. [10], are depicted in Figs. 1, 2. The corresponding values of the remaining parameters b_0 , b_1 , γ , ΔT are given in Table 1.

The solution $\xi(T)$ of Eq. (29) is unique in both cases and minimizes $f(h^{(n,M)}, \beta)$. The graphs of $\xi(T)$ are plotted in Fig. 3.

It appears that higher order terms of the expansions (42), (45) should be included in order to improve the quality of mean-field $\Delta C/c$.

It is worth noting that since the best fitting values M_f of M are much smaller than $A = 6.022 \cdot 10^{23}$, the sample S can be viewed as consisting of magnetic domains, each containing M_f impurities with a definite favoured impurity-spin orientation, which differs, in general, from one domain to another. Existence of such domains in some magnetic materials has been established experimentally (e.g. Ref. [20]).

3.2 (La_{1-x}Ce_x) Al₂


Experimental data on $\Delta C/c$ of (La_{1-x}Ce_x) Al₂ alloys are presented in Ref. [12]. According to Refs. [12, 21], a typical Kondo effect, without any superconducting side-effects, is observed in (La_{1-x}Ce_x) Al₂ samples with Ce content above $x = 0.0067$. However, according to Bader et al. [12], for $x = 0.0064$ the expected normal-state and measured superconducting-state heat capacities do not differ significantly. Thus a mean-field normal-state theory of $\Delta C/c$ for (La_{1-x}Ce_x) Al₂ with $x = 0.0064$ can be reliable.


The number of valence electrons per host atom in LaAl₂ equals 8/3. For a $x = 0.0064$,

$$c = \frac{0.0064}{2.9936} = \frac{4}{1871} \quad , \quad n_1 = \frac{8}{3}c^{-1} = \frac{3742}{3}.$$

Since the spin of Ce ions equals 1/2 [12], therefore

$$f_2(\xi) = \frac{\gamma}{M\sqrt{n_1}} \tanh(\beta\gamma\xi\sqrt{n_1}) \quad (32)$$

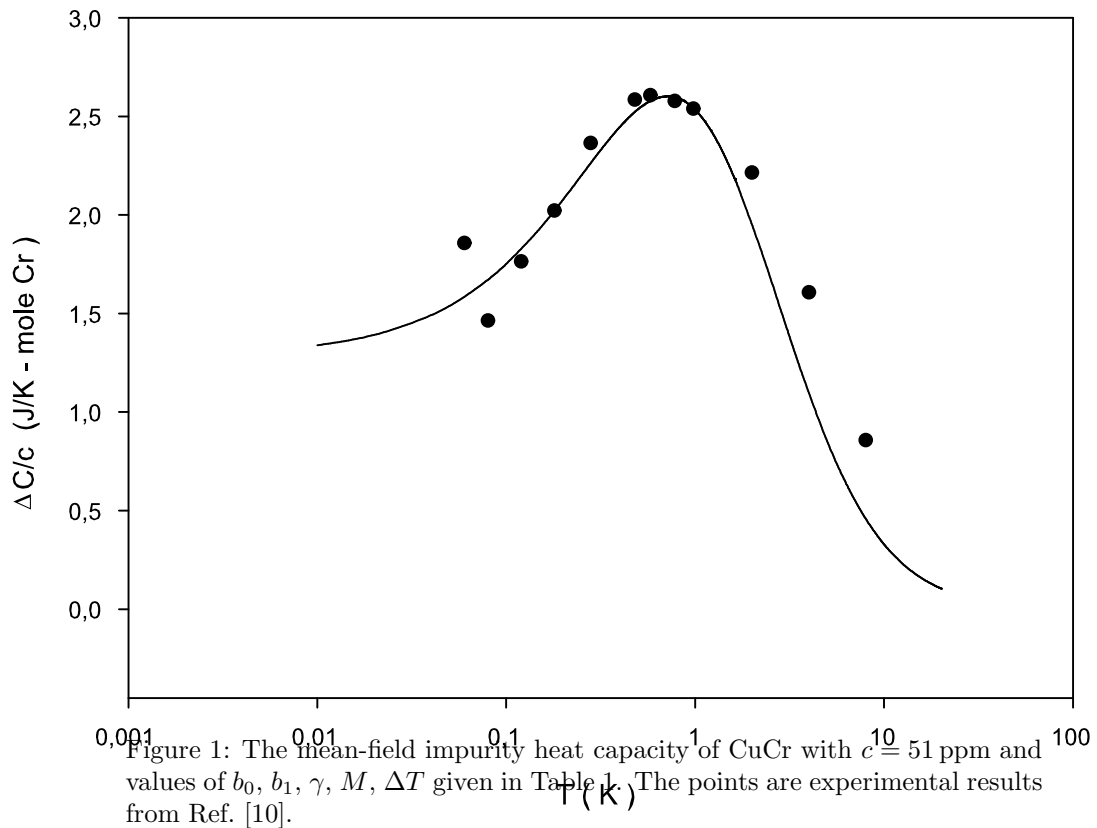

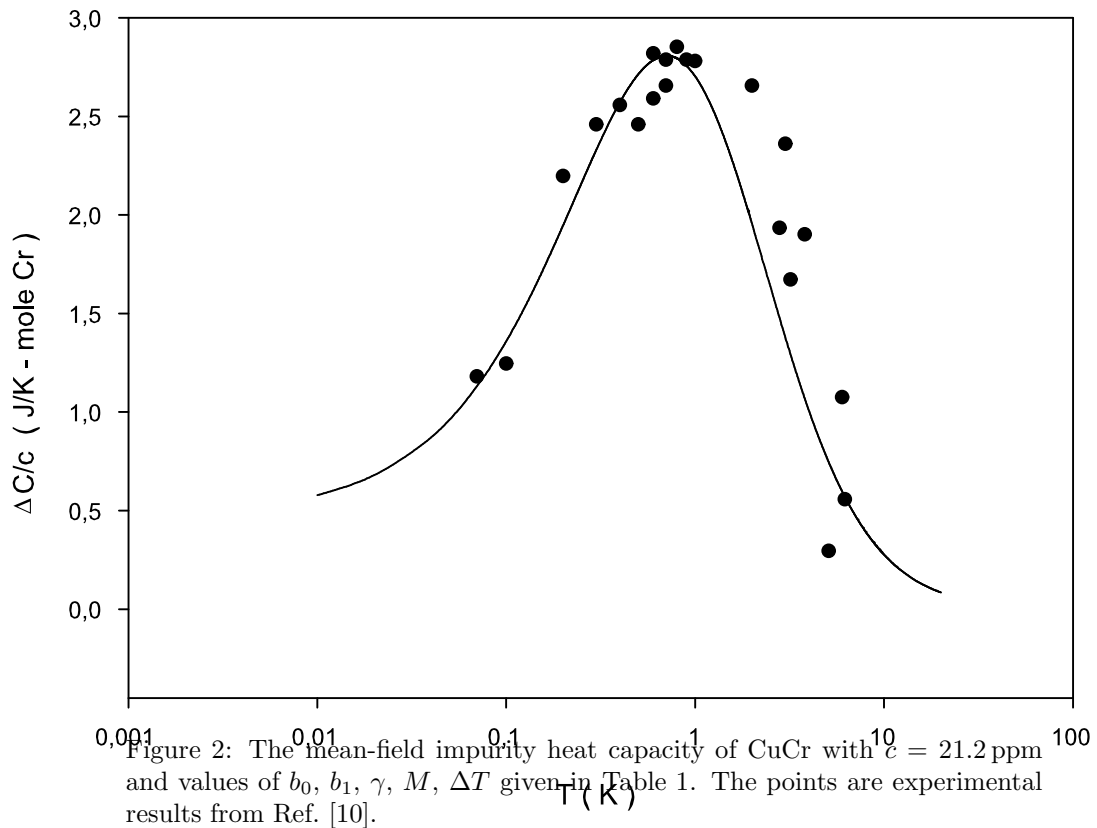

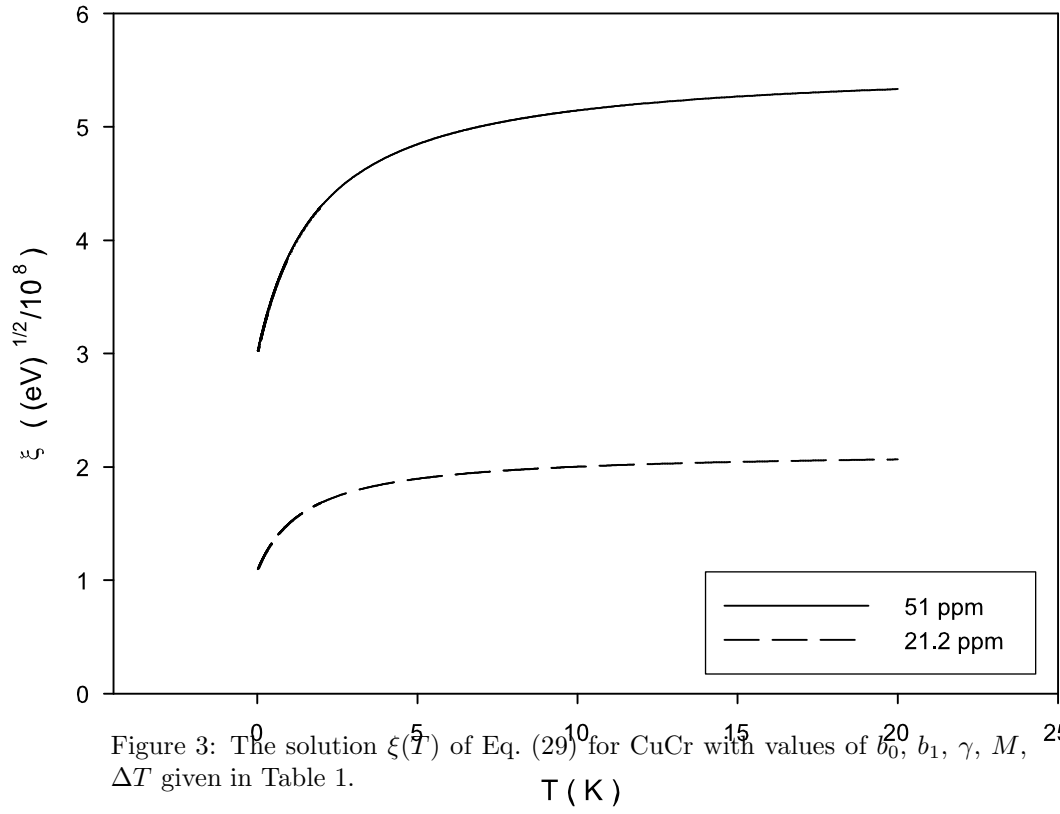


Figure 3: The solution $\xi(T)$ of Eq. (29) for CuCr with values of b_0 , b_1 , γ , M , ΔT given in Table 1.

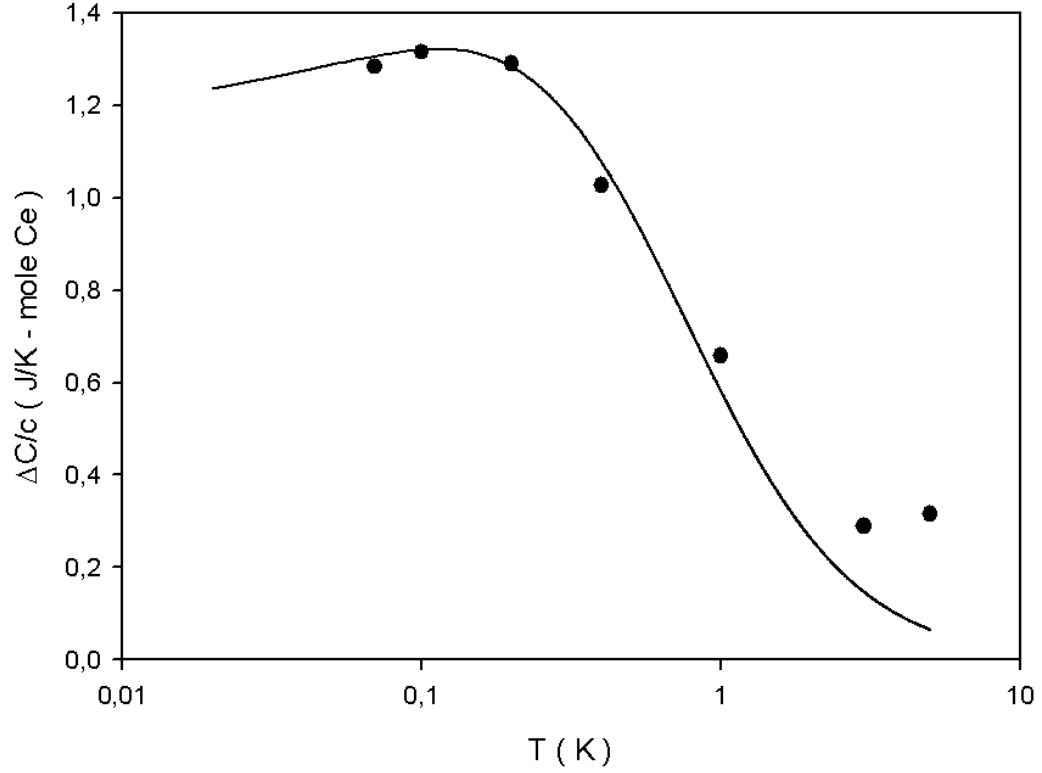


Figure 4: The mean-field impurity heat capacity of $(\text{La}_{1-x}\text{Ce}_x)\text{Al}_2$ with $x = 0.0064$ and values of b_0 , b_1 , γ , M , ΔT given in Table 1. The points are experimental results from Ref. [12].

and $\Delta U_m/c$ for a sample S of $(\text{La}_{1-x}\text{Ce}_x)\text{Al}_2$, expressed in joules, equals

$$c^{-1}\Delta U_m = \left(\frac{1}{2}\gamma^2 - \frac{1}{2}M^2n_1f_2^2(\xi) - M^2n_1f_2(\xi)[b_0 + b_1f_2(\xi) + \dots] \right) \frac{1}{4} \cdot 602.2 \cdot 160.2 \cdot 1871 M^{-1} \quad (33)$$

if Eq. (44) is used and b_0 , γ , β , ξ are given in powers of eV.

The mean-field $\Delta C/c$ curve best fitting to experimental $\Delta C/c$ of Ref. [12] was obtained for $M = 40$ and is depicted in Fig. 4. The corresponding values of other parameters are given in Table 1. Since the error of experimental $\Delta C/c$ values is relatively high above 5 K [12], the mean-field $\Delta C/c$ curve in Fig. 4 provides a good fit to experiment.

The equation $f_3(\xi) = \xi$ for $\xi(T)$ has a unique minimising solution with $\xi(T) \in (11 \cdot 10^{-5} \sqrt{\text{eV}}, 19 \cdot 10^{-5} \sqrt{\text{eV}})$ for $T \in (0.015 \text{ K}, 10 \text{ K})$. The graph of $\xi(T)$ is, similar as those for CuCr in Fig. 3, increasing in T .

4 Concluding remarks

Progress has been made in improving the quality of theoretical impurity heat capacity graphs $\Delta C(T)$ of DMA. Scaling procedures, used in previous s-d theories to adjust thermodynamic functions to experimental data, were unnecessary and nonlinear dependence of $\Delta C(T)$ on impurity concentration c in CuCr has been accounted for the first time.

The mean-field theory of a dilute s-d system established in Ref. [11] has also proved capable of explaining the temperature dependence of impurity heat capacity ΔC of $(\text{La}_{1-x}\text{Ce}_x)\text{Al}_2$ with $x = 0.0064$. Partial quantitative agreement between theory and experiment has been achieved for CuCr alloys, especially for the smaller value of impurity concentration considered.

Higher order terms of the expansion of f_1 should be included in order to improve these results.

A

The integral (15) is an M -fold product of 3-dimensional integrals

$$I = \int_{\Lambda} d^3 R \exp \left[-\frac{1}{2} u_2 \int_0^\beta \sum_{q=1}^3 (R_q - r_{0q} - \omega_q(s))^2 ds \right] \quad (34)$$

and $\exp[-\beta M u_0]$. The representation (16) of $\langle \rho(\vec{r}, \vec{r}') \rangle_{\Lambda}$, for large β , obtains by applying to the I the dominated convergence theorem (in order to express the integral in the exponent as a limit of partial sums) and the method of steepest descent:

$$\begin{aligned} I &= \lim_{m \rightarrow \infty} \int_{\Lambda} d^3 R \exp \left[-\frac{\beta}{2m} u_2 \sum_{k=1}^m \sum_q (R_q - r_{0q} - x_{kq})^2 \right] \\ &\approx \lim_{m \rightarrow \infty} \int_{\mathbb{R}^3} d^3 R \exp \left[-\frac{\beta}{2m} u_2 \sum_{kq} x_{kq}^2 \right. \\ &\quad \left. - \frac{\beta}{2m} u_2 \sum_q \left(\frac{1}{\sqrt{m}} \sum_k x_{kq} - \sqrt{m} (R_q - r_{0q}) \right)^2 + \frac{\beta}{2m^2} u_2 \sum_q \left(\sum_k x_{kq} \right)^2 \right] \\ &= \lim_{m \rightarrow \infty} \left(\frac{2\pi}{\beta u_2} \right)^{3/2} \exp \left[-\frac{\beta}{2m} u_2 \sum_{kq} x_{kq}^2 + \frac{\beta}{2m^2} u_2 \sum_q \left(\sum_k x_{kq} \right)^2 \right] \\ &= \left(\frac{2\pi}{\beta u_2} \right)^{3/2} \exp \left[-\frac{1}{2} u_2 \int_0^\beta \omega^2(s) ds + \frac{1}{2} \beta^{-1} u_2 \sum_q \left(\int_0^\beta w_q(s) ds \right)^2 \right], \end{aligned} \quad (35)$$

where $x_{kq} = \omega_q \left(\frac{k\beta}{m} \right)$. The squared integral in the exponent can be linearized, using the identity

$$\exp(a^2) = (2\pi)^{-1/2} \int_{-\infty}^{\infty} \exp \left[-\frac{1}{2}\xi^2 + \sqrt{2}a\xi \right] d\xi$$

which yields

$$\begin{aligned} I^M &= \left(\frac{2\pi}{\beta u_2} \right)^{3M/2} \exp \left[-\frac{1}{2} M u_2 \int_0^\beta \omega^2(s) ds + \frac{1}{2} \beta^{-1} M u_2 \sum_q \left(\int_0^\beta w_q(s) ds \right)^2 \right] \\ &= (2\pi)^{-3/2} \left(\frac{2\pi}{\beta u_2} \right)^{3M/2} \int_{\mathbb{R}^3} d\xi_1 d\xi_2 d\xi_3 \exp \left[-\frac{1}{2} \sum_s \xi_s^2 \right. \\ &\quad \left. - \frac{1}{2} M u_2 \int_0^\beta \omega^2(s) ds + \sqrt{\beta^{-1} M u_2} \sum_q \xi_q \int_0^\beta \omega_q(s) ds \right] \\ &= \left(\frac{2\pi}{\beta u_2} \right)^{\frac{3}{2}(M-1)} M^{3/2} \int_{\mathbb{R}^3} d\lambda_1 d\lambda_2 d\lambda_3 \exp \left[-\frac{1}{2} M u_2 \sum_q \int_0^\beta (\omega_q(s) - \lambda_q)^2 ds \right] \end{aligned} \quad (36)$$

in accord with Eq. (16).

B

The form of f_1 defined by Eq. (7) is crucial in the mean-field theory of the s-d system. Here f_1 is derived under the assumption that $\tilde{h}_e^{(1,M)}(\xi, \eta)$ is defined in terms of a function $-g\sqrt{n}U \left(|\vec{R}_\alpha - \vec{r}| \right)$, which has absolute maximum equal v_0 and absolute minimum equal u_0 , and that the expansion in (15) is terminated on the first term. The space average of $\exp \left[-\beta \tilde{h}_e^{(1,M)}(\xi, 0) \right]$ over impurity positions then equals

$$\left\langle \exp \left[-\beta \tilde{h}_e^{(1,M)}(\xi, 0) \right] \right\rangle_\Lambda = \begin{cases} \exp \left[-\beta H_0^{(1)} - \beta M u_0 \xi \right] & \text{for } \sigma_z = 1 \\ \exp \left[-\beta H_0^{(1)} + \beta M v_0 \xi \right] & \text{for } \sigma_z = -1 \end{cases}$$

and Eq. (10) for z takes the form

$$\begin{aligned} \frac{4\pi v}{h^3} \int_0^\infty dp p^2 \left\{ \left(z^{-1} \exp \left[\beta \left(M u_0 \xi + \frac{p^2}{2m} \right) \right] + 1 \right)^{-1} \right. \\ \left. + \left(z^{-1} \exp \left[\beta \left(-M v_0 \xi + \frac{p^2}{2m} \right) \right] + 1 \right)^{-1} \right\} = 1, \end{aligned} \quad (37)$$

where $v = |\Lambda|n^{-1}$. Following Huang [22], one transforms Eq. (37) to

$$v\lambda_0^{-3} (f_{3/2}(ze^{-\beta Mu_0\xi}) + f_{3/2}(ze^{\beta Mv_0\xi})) = 1, \quad (38)$$

where

$$v\lambda_0^{-3} = \frac{1}{8}3\sqrt{\pi}(\beta\varepsilon_F)^{-3/2}.$$

For large z , $f_{3/2}(z)$ is given by Sommerfeld's expansion:

$$f_{3/2}(z) = \frac{4}{3\sqrt{\pi}} \left((\ln z)^{3/2} + \frac{\pi^2}{8} (\ln z)^{-1/2} + \dots \right). \quad (39)$$

Let $Mu_0\xi\varepsilon_F^{-1} = \mu$, $Mv_0\xi\varepsilon_F^{-1} = \nu$. Then z satisfying Eq. (38) is given by the expansion

$$\ln z = a_1\beta\varepsilon_F + a_0 + a_{-1}(\beta\varepsilon_F)^{-1} + \dots \quad (40)$$

with

$$a_1(\xi) = 1 + \frac{1}{2}(\mu - \nu) - \frac{1}{16}(\mu + \nu)^2 + \dots$$

$$a_0 = 0$$

$$a_{-1}(\xi) = -\frac{\pi^2}{12} \left(1 - \frac{1}{4}(\mu + \nu)^2 \right)^{-1/2} = -\frac{\pi^2}{12} \left(1 + \frac{1}{8}(\mu + \nu)^2 + \dots \right).$$

From Eq. (7) one finds (cf. Ref. [11])

$$f_1(\xi) = (Mn\beta)^{-1} \frac{\partial}{\partial \xi} \text{Tr} \ln (1 + z\rho^{(1)}).$$

Hence

$$f_1(\xi) = v\lambda_0^{-3} (-u_0 f_{3/2}(ze^{-\beta Mu_0\xi}) + v_0 f_{3/2}(ze^{\beta Mv_0\xi}))$$

$$= b_0 + b_1\xi - \frac{\pi^2}{8}b_0(\beta\varepsilon_F)^{-2} + \dots \quad (41)$$

with

$$b_0 = \frac{1}{2}(v_0 - u_0) \quad , \quad b_1 = \frac{3M}{8\varepsilon_F}(u_0 + v_0)^2.$$

The energy of the electrons' subsystem also expresses in terms of f_1 . According to Eqs. (3b), (7)

$$\left\langle n\Gamma_1^n \tilde{h}_e^{(1,M)}(\xi, \eta) \right\rangle_{n\Gamma_1^n \tilde{h}_e^{(1,M)}(\xi, \eta)}$$

$$= \left\langle n\Gamma_1^n H_0^{(1)} \right\rangle_{n\Gamma_1^n \tilde{h}_e^{(1,M)}(\xi, \eta)} - nM f_2(\xi) (b_0 + b_1 f_2(\xi) + \dots) \quad (42)$$

The first term on the rhs of Eq. (42) can be evaluated in a similar manner as the energy of a free Fermi gas, viz.,

$$\begin{aligned}
& \left\langle n\Gamma_1^n H_0^{(1)} \right\rangle_{n\Gamma_1^n \tilde{h}_e^{(1,M)}(\xi, \eta)} \\
&= \frac{3n}{10} \varepsilon_F^{-3/2} \beta^{-5/2} \left\{ (\ln z - \beta M u_0 (\xi - \eta))^{5/2} \right. \\
&+ \frac{5}{8} \pi^2 (\ln z - \beta M u_0 (\xi - \eta))^{1/2} + \dots \\
&+ (\ln z + \beta M v_0 (\xi - \eta))^{5/2} + \frac{5}{8} \pi^2 (\ln z + \beta M v_0 (\xi - \eta))^{1/2} + \dots \left. \right\} \\
&= \frac{3n}{10} \varepsilon_F \left\{ 2 + 5a_{-1} (\xi - \eta) (\beta \varepsilon_F)^{-2} + \frac{5}{4} \pi^2 (\beta \varepsilon_F)^{-2} \right. \\
&+ \frac{5}{8} M^2 (u_0 + v_0)^2 \varepsilon_F^{-2} (\xi - \eta)^2 + \dots \left. \right\} \\
&= \left\langle n\Gamma_1^n H_0^{(1)} \right\rangle_{n\Gamma_1^n H_0^{(1)}} - \frac{\pi^2}{24} n M b_1 (\xi - \eta)^2 (\beta \varepsilon_F)^{-2} + \frac{1}{2} n M b_1 (\xi - \eta)^2 + \dots
\end{aligned} \tag{43}$$

If the Taylor expansions of $U_\alpha(\vec{r})$ around the absolute maximum and absolute minimum are cut off on the second derivatives, the structure of f_1 , as well as that of the expectation values (42), (43), changes, e.g. under the approximations of Section 2, f_1 is no longer regular at $\xi = 0$:

$$\begin{aligned}
f_1(\xi) = v \left\{ \lambda_0 (t(u_2, \beta))^{-3} \frac{\partial Z_0(u_0 \xi, u_2 \xi)}{\partial \xi} f_{3/2}(z Z_0(u_0 \xi, u_2 \xi)) \right. \\
\left. + \lambda_0 (t(-v_2, \beta))^{-3} \frac{\partial Z_0(-v_0 \xi, -v_2 \xi)}{\partial \xi} f_{3/2}(z Z_0(-v_0 \xi, -v_2 \xi)) \right\},
\end{aligned}$$

with

$$v \lambda_0^{-3}(t) = \frac{1}{8} 3 \sqrt{\pi} (t \varepsilon_F)^{-3/2}$$

(u_2 (v_2) denoting the second derivative of $-g\sqrt{n}U(\vec{R}_\alpha - \vec{r})$ at the absolute minimum (maximum)) and the corresponding coefficient b'_1 , in the new expansion of f_1 around $\xi_0 \neq 0$, will differ from b'_1 resulting in the modified Eq. (43). In view of the presumable smallness of

$$\Delta U_0 = \left\langle n\Gamma_1^n H_0^{(1)} \right\rangle_{\tilde{h}_e^{(n,M)}(\xi, \eta)} - \left\langle n\Gamma_1^n H_0^{(1)} \right\rangle_{n\Gamma_1^n H_0^{(1)}}$$

where $\tilde{h}_e^{(n,M)} = n\Gamma_1^n \tilde{h}_e^{(1,M)}$, these modifications can be exploited in the simplest manner by restricting u_0 , v_0 , u_2 , v_2 to values for which b'_1 vanishes. As a consequence,

$$\Delta U_0 \approx 0 \tag{44}$$

whereas the range of b'_1 can be expected to include also negative values. Thus, in general,

$$f_1(\xi) = b'_0 + b'_1 \xi + \dots \quad , \quad b'_0, b'_1 \in \mathbb{R}^1 \tag{45}$$

References

- [1] J. Kondo. *Prog. Theor. Phys.*, 32:37, 1964.
- [2] P. E. Bloomfield and D. R. Hamann. *Phys. Rev.*, 164:856, 1967.
- [3] K. G. Wilson. *Rev. Mod. Phys.*, 47:773, 1975.
- [4] V. T. Rajan, J. H. Lowenstein, and N. Andrei. *Phys. Rev. Lett.*, 49:497, 1982.
- [5] N. Andrei, K. Furuya, and J. H. Lowenstein. *Rev. Mod. Phys.*, 55:331, 1983.
- [6] V. M. Filyov, A. M. Tsvelik, and P. B. Wiegmann. *Phys. Lett. A*, 81:115, 1981.
- [7] P. B. Wiegmann. An exact solution of the Kondo problem. In I. M. Lifshits, editor, *Quantum Theory of Solids*. MIR Publishers, Moscow, 1982.
- [8] A. C. Hewson. *The Kondo Problem to Heavy Fermions*. Cambridge University Press, Cambridge, 1993.
- [9] J. Maćkowiak. *Phys. Rep.*, 308:235, 1999.
- [10] B. B. Triplett and N. E. Philips. *Phys. Rev. Lett.*, 27:1001, 1971.
- [11] J. Maćkowiak. *Physica A*, 336:461, 2004.
- [12] S. D. Bader, N. E. Philips, M. B. Maple, and C. A. Luengo. *Solid State Commun.*, 16:1263, 1975.
- [13] B. Simon. *Functional Integration and Quantum Physics*. Academic Press, New York, San Francisco, London, 1979.
- [14] J. Glimm and A. Jaffe. *Quantum Physics, A Functional Integral Point of View*. Springer, New York, Heidelberg, Berlin, 1981.
- [15] S. F. Edwards. *Phil. Mag.*, 3:1020, 1958.
- [16] V. Ambegaokar. The Green's Function Method. In R. D. Parks, editor, *Superconductivity*. Marcel Dekker, Inc., New York, 1969.
- [17] J. M. Ziman. *Principles of the Theory of Solids*. Cambridge University Press, Cambridge, 1972.
- [18] S. Pruski and J. Maćkowiak. *Rep. Math. Phys.*, 1:309, 1971.
- [19] P. Monod and S. Schultz. *Phys. Rev.*, 173:645, 1968.
- [20] A. Aharoni. *Introduction to the Theory of Ferromagnetism*. Oxford University Press, 2000.
- [21] W. Felsch, K. Winzer, and G. V. Minnigerode. *Z. Physik B*, 21:151, 1975.
- [22] K. Huang. *Statistical Mechanics*. Wiley Inc., New York, London, 1963.